

### **DELO-DUALBOND® LT354**

UV- heatcuring adhesive

#### **Base**

- dual-curing modified polycarbaminacid derivative
- one-component, solvent-free, UV- heatcuring, filled

#### **Use**

- especially for a fast fixing of components an curing at low temperatures
- the cured product is normally used in a temperature range of -40 °C to +130 °C; depending on the application, other limits may be more reasonable
- compliant with RoHS directive 2015/863/EU
- halogen-free by the criteria of IEC 61249-2-21

#### **Processing**

- the adhesive is supplied ready for use; in case refrigerated storage, it must be ensured that the container is conditioned to room temperature before use
- the containers are conditioned at room temperature (max. +25 °C); the conditioning time is approx. 0.5 h for containers up to 10 ml, 1 h for containers up to 50 ml; additional heat addition is not allowed
- for DELO-FLEXCAP containers the conditioning time is 1 h for the 10 ml and 2 h for the 30 ml version
- the surfaces to be bonded must be dry as well as free of dust, grease an other contaminations
- dispensing valves and product-bearing elements must be carefully cleaned directly after adhesive use
- adequate cleaners are acetone and BDGA (butyldiglykolacetate); for BDGA use acetone as a chaser, do not use alcoholic or hydrous cleaners

## Curing


- fixing by curing with UVA light in a wavelength range of 320 nm - 420 nm in 1 - 5 seconds. Curing by heat in a temperature range of +80 °C to +130 °C is mandatory
- the predominant part which has to be bonded should not get fixed with light, the maximum adhesion is given with an only heat cured product
- the time between fixing and heat curing should not be longer than 1 hour at room temperature (max. +25 °C)
- the adhesive features a post-curing attitude. After a heat curing step at low temperatures (< +120 °C) and a short curing time a strength is given. Furthermore the adhesive shows a post curing at room temperature and rises up to the strength after about 24 h recording to the temperature of the heat curing step
- the actual curing times at the respective temperatures are dependent on the heating time of the components, the heating time of the components must be added to the curing time of the adhesive
- the heating time depends on the component size and the oven type

Lamp type	DELOLUX		
Wavelength [nm]	365	400	460
Suitability	++	+	-

- not suitable + suitable ++ especially suitable

## Absorption spectrum

- photoinitiation system in mCD basic matrix

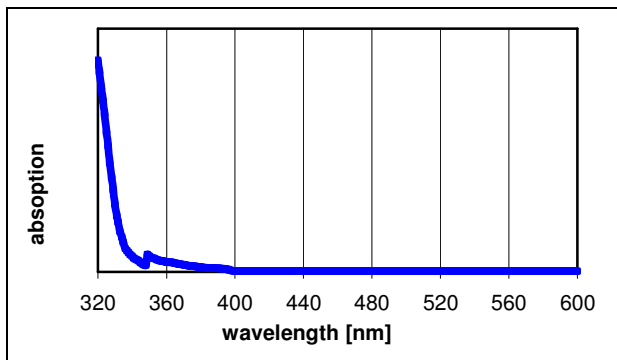

## Technical data

<i>Color</i>	dark gray
Filler	minerals
Density [g/cm <sup>3</sup> ] DELO standard 13	1.3
<i>Viscosity</i> [mPas] at 23 °C, rheometer, shear rate 10 1/s	75000
Thixotropy index	4.9
Processing time [h] at room temperature (max. 25 °C)	72
fixing time by light [s] UVA 365 nm, intensity: 55 - 60 mW/cm <sup>2</sup> DELOLUXcontrol	1 - 5
Curing time with air convection oven [min] at +80 °C	30
Curing time with air convection oven [min] at +90 °C	20

Curing time with air convection oven [min] at +100 °C	10
Compression shear strength glass/glass [MPa] DELO Standard 5 curing: 50 min at +100 °C after 24 h room temperature	42
Compression shear strength PC/PC [MPa] DELO Standard 5 curing: 50 min at +100 °C after 24 h room temperature	41
Compression shear strength FR4/FR4 [MPa] DELO Standard 5 curing: 10 min at +130 °C curing time: 24 h at room temperature (approx. 23 °C)	36
<i>Compression shear strength Al/Al</i> [MPa] DELO Standard 5 curing: 50 min at +100 °C after 24 h room temperature	26
Compression shear strength LCP/LCP (E130i) [MPa] DELO Standard 5 curing: 50 min at +100 °C after 24 h room temperature	10
Tensile strength [MPa] according to DIN EN ISO 527 layer thickness: 2 mm curing: 50 min +100 °C after 24h room temperature (max. +25 °C)	15
Elongation at tear [%] according to DIN EN ISO 527 layer thickness: 2 mm curing: 50 min at +100 °C after 24 h room temperature	20
Young's modulus [MPa] according to DIN EN ISO 527 layer thickness: 2 mm curing: 50 min +100 °C after 24h room temperature (max. +25 °C)	500
Shore hardness D according to DIN EN ISO 868	72
Glass transition temperature [°C] TMA, DELO Standard 28	80
Coefficient of linear expansion [ppm/K] DELO Standard 26 TMA in a temperature range of +55 °C to +70 °C	150
Coefficient of linear expansion [ppm/K] DELO Standard 26 TMA in a temperature range of +95 °C to +120 °C	179
Shrinkage [vol. %] DELO Standard 13	2.4
Water absorption [%] according to DIN EN ISO 62 after 50 min at +100 °C	0.24
storage life at -18°C in unopened original container	6 months

## **Instructions and advice**

### **General**

The data and information provided are based on tests performed under laboratory conditions. Reliable information about the behavior of the product under practical conditions and its suitability for a specific purpose cannot be concluded from this. It is the customer's responsibility to test the suitability of the product for the intended purpose by considering all specific requirements. Type and physical and chemical properties of the materials to be processed with the product, as well as all actual influences occurring during transport, storage, processing and use, may cause deviations in the behavior of the product compared to its behavior under laboratory conditions. The data and information provided are therefore no guarantee for specific product properties or the suitability of the product for the intended purpose.

Nothing contained herein shall be construed to indicate the non-existence of any relevant patents or to constitute a permission, encouragement or recommendation to practice any development covered by any patents, without permission of the owner of this patent.

All products provided by DELO are subject to DELOs' General Terms of Business. Verbal side agreements are not permitted. This document is subject to change.

### **Instructions for use**

The instructions for use of DELO-DUALBOND are available on: [www.DELO.de](http://www.DELO.de). We will be pleased to send them to you on demand.

### **Occupational health and safety**

see material safety data sheet

### **Specification**

The properties in italics are part of the specification. Ranges with clear limits are defined for them and others, where applicable. In the course of the QA test, each batch is tested for these properties and the maintenance of the limits is ensured. The measuring methods used can deviate from those specified in the data sheet. Details can be found in the QA test report.